



U.S. Army Research Institute of Environmental Medicine

Natick, Massachusetts

TECHNICAL REPORT NO. T18-02

DATE March 2018

**COMPARISON OF COLD WEATHER CLOTHING BIOPHYSICAL PROPERTIES:
US ARMY, CANADIAN DEPARTMENT OF NATIONAL DEFENCE, AND
NORWEGIAN MILITARY**

Approved for Public Release; Distribution Is Unlimited

**United States Army
Medical Research & Materiel Command**

DISCLAIMER

The opinions or assertions contained herein are the private views of the author(s) and are not to be construed as official or reflecting the views of the Army or the Department of Defense. The investigators have adhered to the policies for protection of human subjects as prescribed in 32 CFR Part 219, Department of Defense Instruction 3216.02 (Protection of Human Subjects and Adherence to Ethical Standards in DoD-Supported Research) and Army Regulation 70-25. Human subjects participated in these studies after giving their free and informed voluntary consent. Any citations of commercial organizations and trade names in this report do not constitute an official Department of the Army endorsement or approval of the products or services of these organizations.

USARIEM TECHNICAL REPORT T18-02

**COMPARISON OF COLD WEATHER CLOTHING BIOPHYSICAL PROPERTIES:
US ARMY, CANADIAN DEPARTMENT OF NATIONAL DEFENCE, AND
NORWEGIAN MILITARY**

Adam W. Potter ^{1, 2}
Julio A. Gonzalez ¹
Alyssa J. Carter ³
David P. Looney ¹
Timothy P. Rioux ¹
Shankar Srinivasan ²
Wendy Sullivan-Kwantes ⁴
Xiaojiang Xu ¹

¹ Biophysics and Biomedical Modeling Division, USARIEM, Natick, MA

² Rutgers University, School of Biomedical and Health Sciences, Newark, NJ

³ Research Support Division, USARIEM, Natick, MA

⁴ Toronto Research Centre Defence Research and Development Canada (DRDC),

March 2018

U.S. Army Research Institute of Environmental Medicine
Natick, MA 01760-5007

| | | | | | | |
|---|-------------|-----------------------|---------------------------------------|------------------------------------|---|--|
| REPORT DOCUMENTATION PAGE | | | | | <i>Form Approved OMB No. 0704-0188</i> | |
| <small>The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.</small> | | | | | | |
| PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS. | | | | | | |
| 1. REPORT DATE (DD-MM-YYYY) | | 2. REPORT TYPE | | | 3. DATES COVERED (From - To) | |
| 4. TITLE AND SUBTITLE | | | | 5a. CONTRACT NUMBER | | |
| | | | | 5b. GRANT NUMBER | | |
| | | | | 5c. PROGRAM ELEMENT NUMBER | | |
| 6. AUTHOR(S) | | | | 5d. PROJECT NUMBER | | |
| | | | | 5e. TASK NUMBER | | |
| | | | | 5f. WORK UNIT NUMBER | | |
| 7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) | | | | | 8. PERFORMING ORGANIZATION REPORT NUMBER | |
| 9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) | | | | | 10. SPONSOR/MONITOR'S ACRONYM(S) | |
| | | | | | 11. SPONSOR/MONITOR'S REPORT NUMBER(S) | |
| 12. DISTRIBUTION/AVAILABILITY STATEMENT | | | | | | |
| 13. SUPPLEMENTARY NOTES | | | | | | |
| 14. ABSTRACT | | | | | | |
| 15. SUBJECT TERMS | | | | | | |
| 16. SECURITY CLASSIFICATION OF: | | | 17. LIMITATION OF ABSTRACT | 18. NUMBER OF PAGES | 19a. NAME OF RESPONSIBLE PERSON | |
| a. REPORT | b. ABSTRACT | c. THIS PAGE | | | 19b. TELEPHONE NUMBER (Include area code) | |

TABLE OF CONTENTS

| <u>Section</u> | <u>Page</u> |
|---|-------------|
| List of Figures..... | iv |
| List of Tables..... | iv |
| Acknowledgments | v |
| Executive Summary | 1 |
| Introduction | 2 |
| Characterizing Cold Injuries | 3 |
| Purpose and Approach..... | 4 |
| Methods | 5 |
| Biophysical Assessments | 5 |
| Ensembles..... | 5 |
| Insulation Required..... | 7 |
| Duration Limited Exposure | 8 |
| Heat Stress..... | 9 |
| Results | 9 |
| Biophysical Results | 9 |
| Insulation Required..... | 12 |
| Duration Limited Exposure | 15 |
| Heat Stress..... | 17 |
| Discussion..... | 18 |
| References..... | 20 |
| Appendix A..... | 24 |
| US Army Extended Cold Weather Clothing Elements | 24 |
| Canadian Cold Weather Clothing Elements | 27 |
| Norwegian Cold Weather Clothing Elements | 31 |

LIST OF FIGURES

| <u>Figure</u> | | <u>Page</u> |
|---------------|--|-------------|
| 1 | Incidences of Cold Injuries, Active U.S. Army 1997-2017 | 3 |
| 2 | Incidences of Cold Injuries, by type, Active U.S. Army 1997-2017 | 3 |
| 3 | Outline of minimum insulation required ($IREQ_{min}$) for various environmental conditions and work intensities [33] | 8 |
| 4 | Outline of duration limited exposure (DLE) across cold environments for 4 levels of total clothing insulation (clo) at one work intensity [33] | 9 |
| 5 | Thermal insulation (clo) and evaporative potential (i_m/clo) for each ensemble | 11 |
| 6 | Ranking of clothing ensembles based on thermal insulation (clo) | 11 |
| 7 | Ranking of clothing ensembles based on evaporative potential (i_m/clo) | 12 |
| 8 | Compared insulation (clo) values to guidance required ($IREQ_{min}$ and $IREQ_{neutral}$) for three environments during rest | 14 |
| 9 | Compared insulation (clo) values to guidance required ($IREQ_{min}$ and $IREQ_{neutral}$) for three environments during moderate activity (2 MET). | 14 |
| 10 | Duration limited exposure (DLE) by ensemble for three environments (-10, -20, and -30°C during rest and moderate activity (2 MET) | 16 |
| 11 | Compared heat stress over a 120 minutes in a cold environment (10°C) at a moderate work rate (191 W/m ²) | 17 |
| 12 | Levels of clothing system testing | 19 |

LIST OF TABLES

| <u>Table</u> | | <u>Page</u> |
|--------------|---|-------------|
| 1 | Ensemble descriptions | 6 |
| 2 | Biophysical measures for each ensemble | 10 |
| 3 | Calculated Insulation Required by Environment: resting and moderate activity | 12 |
| 4 | Ensemble comparison to guidance requirements for resting and moderate activity in three environmental conditions | 13 |
| 5 | Duration limited exposure (DLE) by ensemble for three environments (-10, -20, and -30°C during rest and moderate activity (2 MET) | 15 |

ACKNOWLEDGMENTS

The authors would like to thank Mr. Anthony Karis for working on some of the initial testing and coordination of cold weather clothing ensembles. The authors would also like to thank Drs Karl Friedl and Reed Hoyt for providing scientific expertise, supervision, and mentorship.

EXECUTIVE SUMMARY

This report provides quantitative biophysical assessments of current cold weather clothing ensembles used by the US Army, the Canadian Department of National Defence, and the Norwegian military. Standard tests for the thermal and evaporative resistances (R_t and R_{et}) were conducted for 22 military cold weather ensembles (9 United States (US), 8 Canadian (CA), and 5 Norwegian (N)) within climate controlled environmental chambers. Total thermal resistance (insulation) in clo units, the vapor permeability index (i_m), and the evaporative potential (i_m/clo) were calculated from R_t and R_{et} measurements. Simple comparisons of the measured values for each of the ensembles was made as well as predicted performances based on modeling of insulation required to maintain safe exposure times.

Simple descriptive statistics were computed for all ensembles, and for each country independently. Total measured biophysical values (mean \pm SD; min-max) for the 22 ensembles were: R_t : 0.312 ± 0.083 ; 0.201-0.482, clo: 2.011 ± 0.533 ; 1.296-3.109, R_{et} : 46.831 ± 11.431 ; 23.5-67.77, i_m : 0.407 ± 0.062 ; 0.313-0.549, i_m/clo : 0.215 ± 0.064 ; 0.139-0.4. Ranking by level of clo showed Canadian and US ensembles (CA 6 and US 4) provide the highest level of thermal insulation; indicating higher protection from extreme cold weather extremes based on low activity or resting conditions. In contrast to levels of thermal insulation, the US Army ensembles, US 1 and US 2 provide the highest evaporative potential (i_m/clo) values, indicating reduced likelihood of imposed heat strain.

The use of simplified standard methods of modeling for three environmental conditions (-10, -20, and -30°C) was used to provide guidance levels of insulation required. The insulation required minimum and neutral ($IREQ_{min}$ and $IREQ_{neutral}$) were used to calculate the minimal and ideal amounts of insulation needed to maintain thermal balance (minimum) and to maintain an equilibrium balance (neutral). From these methods, none of the current ensembles meets the minimum required insulation for resting; or for moderate (2 MET) work in -30°C conditions. Only one ensemble (CA 6) meets the neutral ($IREQ_{neutral}$) criteria for -20°C conditions; while at moderate (2 MET) work rate several ensembles meet the minimal or neutral ($IREQ_{min}$; $IREQ_{neutral}$) values for -10°C conditions

Heat stress modeling was conducted for each ensemble to provide a contrast of thermal burden and as an indication of the potential for increased sweating. Modeled heat stress in cold environmental conditions and moderate work rate showed the noticeable differences over a two hour period across uniforms. At the two hour mark, an absolute difference of 0.85 °C could be observed between the least (US 1) and most (US 4) thermally burdensome uniforms, with a standard deviation of 0.24 across all ensembles.

INTRODUCTION

US Armed Service members operate in a wide array of areas, under many different environmental conditions, and conduct varied and dynamic activities. Given these complex settings, the individuals within the Armed Forces constantly face the threat of succumbing to heat or cold related injuries [1-3].

In a recent report from Berko et al., [4], an analysis of weather related deaths in the U.S. between 2006 and 2010 showed the incidences of weather related deaths to be approximately 2,000 annually (10,649 total for the period). Interestingly, cold related deaths (e.g., hypothermia) were twice as prevalent (63%; n = 6,660) than that of heat related deaths (e.g., heat stroke) (31%; n = 3,332); while other weather events (floods, storms, lightning) accounted for the last six percent (n = 662).

Exposure to natural weather events, such as extreme heat or cold, is a national and international concern. However, this is even more of an acute issue for the U.S. military, as they routinely travel and conduct a range of physical activities around the world within the full spectrum of extreme environmental conditions. Furthermore, the complexity of military operations and activities within this range of environments is more dynamic than that of civilian exposure events.

Figure 1 outlines the cold injury incidences for active duty members of the U.S. Army using a collection of published reports from the Medical Surveillance Monthly Report (MSMR) over a 20 year period [5-22]. From 1997 to 2017, the total reported incidences of clinically reported cold injuries for the active duty U.S. military is broken out into four main areas: frostbite, immersion foot and hand, hypothermia, and unspecified. The instances are shown as number of cases (n) and rate (per 100,000 person-years (p-yrs)); where frostbite (n=3,323; 33.3 p-yrs), immersion foot (n=839; 8.4 p-yrs), hypothermia (n=648; 6.4 p-yrs), and unspecified (n=1,873; 18.9 p-yrs), totaling 6,683; 67.5 p-yrs (Figure 2).

Figure 1. Incidences of Cold Injuries, Active U.S. Army 1997-2017


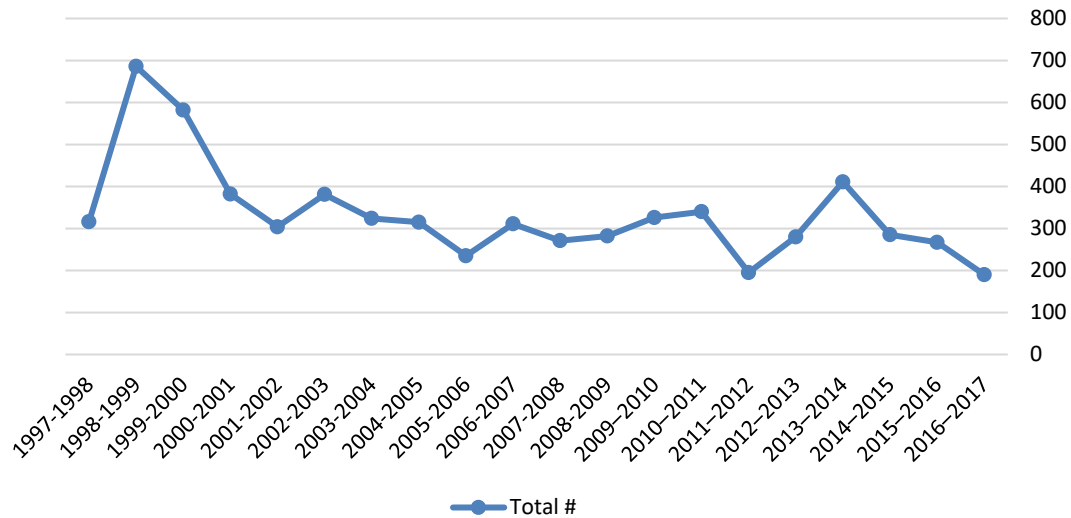


Figure 2. Incidences of Cold Injuries, by type, Active U.S. Army 1997-2017

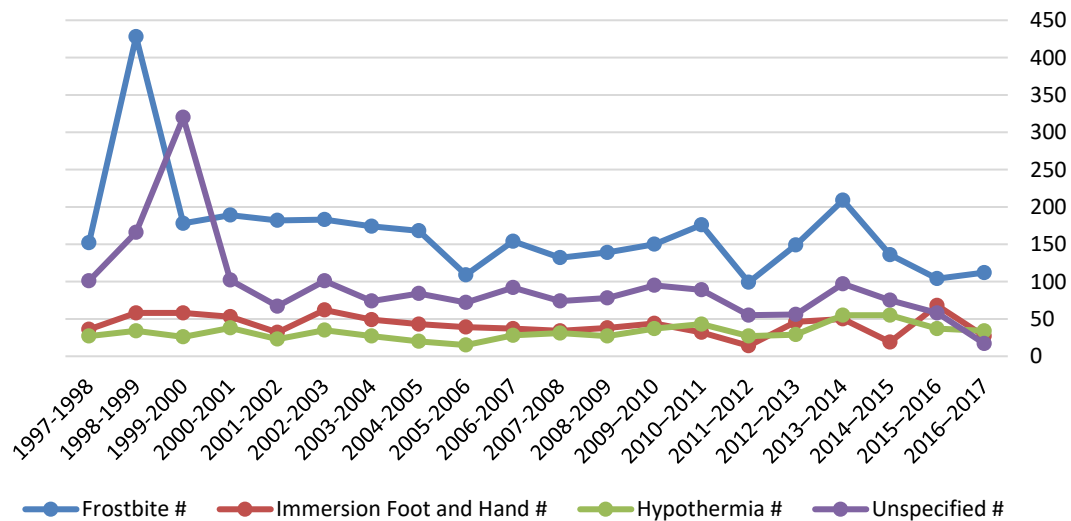

Characterizing Cold Injuries

Characterizing cold related injuries is fairly complex, as the responses to cold have higher individual variability when compared to that of heat related injuries. From a clinical perspective, cold related injuries can be broadly binned into three categories: frostbite, nonfreezing cold injuries, and hypothermia. In addition, each of these has varying levels of severity and subcategories associated to them.

Frostbite is below the point at which skin tissue begins to freeze. While 0°C (32°F) is traditionally considered the freezing point of water, the freezing point of skin is understood to be marginally less due to electrolytes [23]. Observed freezing points range from as low as -4.8°C to as high as -0.6°C [23-24].

Nonfreezing cold injuries include an array of injury events where tissue freezing has not occurred but damage occurs. The level of severity of nonfreezing injuries is determined by the temperature, duration, and wetness of the exposure to the tissue. Four of the more common specific types of nonfreezing injuries include immersion (trench) foot, chilblain, cold urticaria, and cold-induced bronchoconstriction [25]. Immersion foot is a nonfreezing injury where the foot becomes swollen, the skin is red initially but as severity increases the skin becomes lower in oxygen saturation and becomes cyanotic (purple, bluish discoloration) [23, 25]. Immersion foot is most often reported after tissue have been exposed for extended periods of time to non-freezing temperatures, between 0-15°C (32-60°F) [25]. The 'immersion' term itself refers to when the foot is actually immersed but more typically when the foot becomes immersed and remains wet within boots [23, 25]. Chilblains is considered a fairly common nonfreezing injury that appears as more superficial than immersion foot and occurs due to shorter term exposure (i.e., 1-5 hours) of temperatures below 16°C (60°F) [23]. Cold urticaria is expressed as a quick onset of redness, swelling and itchiness of the skin in response to short-term exposure (i.e., minutes) to cold environments [25]. Cold-induced bronchoconstriction is a physiological response where an individual's airways are narrowed during exercise in cold environments [23, 25-27].

Hypothermia as a broad category of cold injury is clinically described to be the point at which core body temperature has dropped below 35°C (95°F) [28]. However, hypothermia is more specifically defined with four levels of severity; where normothermia (normal temperature level) is approximately 37°C (98.6°F), mild hypothermia is between 35.0 – 36.0°C (95.0 – 96.8°F), moderate hypothermia being 32.0 – 35.0°C (89.6 – 95.0°F), and severe hypothermia being 28.0 – 32.0°C (82.4 – 89.6°F) [23,28]. Table 2 outlines specific core temperature reference points associated with physiological changes / responses using work by Castellani et al., [23] and Pozos and Danzl [28].

Purpose and Approach

Clothing protects the wearer from environmental threats, e.g., hot or cold exposure. In order to understand the protection provided by specific clothing ensembles thermal sweating manikins have been historically used to provide quantitative assessments of the heat transfer (biophysical) properties of clothing ensembles, namely thermal and evaporative resistance (R_t and R_{et}).

This report provides quantitative biophysical assessments of the current cold weather clothing ensembles used by the US Army, the Canadian Department of National Defence, and the Norwegian military.

METHODS

Biophysical Assessments

Standard tests for the thermal and evaporative resistances (R_t and R_{et}) were conducted (ASTM F1291-16 & ASTM F2370-16) [29-30] for 22 military cold weather ensembles (9 United States (US), 8 Canadian (CA), and 5 Norwegian (N)) within climate controlled environmental chambers (Table 1; Appendix A). Each of the 22 ensembles varied in the types of material and number of layers.

Measures obtained for analysis included:

- thermal resistance (R_t) (Eq. 1)
- R_t is converted into units of clo (Eq. 2)
- evaporative resistance (R_{et}) (Eq. 3)
- R_t and R_{et} is converted into a vapor permeability index (i_m) (Eq. 4)
- together i_m and clo (i_m/clo) is used to represent evaporative potential [31-32]

Thermal resistance (R_t) is the dry heat transfer from the surface of the manikin through the clothing and into the environment, mainly from convection; where T_s is surface temperature, T_a is the air temperature in °C or K; Q is power input (W) to maintain the surface (skin) temperature (T_s) of the manikin at a given set point; A is the surface area of the measurement in m^2 . Measures of R_t can then be converted to units of clo, where I_t is the total insulation including boundary air layers. Evaporative resistance (R_{et}) is heat loss from the body in isothermal conditions ($T_s \approx T_a$); where P_{sat} is vapor pressure in Pascal at the surface of the manikin (assumed to be fully saturated), and P_a is vapor pressure, in Pascal, of the chamber environment. Measures of R_t and R_{et} can then be used to calculate the vapor permeability index (i_m), a non-dimensional measure of water vapor resistance of materials.

$$R_t = \frac{(T_s - T_a)}{Q/A} [\text{m}^2 \text{K/W}] \quad \text{Eq 1.}$$

$$\text{clo} = 6.45(R_t) \quad \text{Eq 2.}$$

$$R_{et} = \frac{(P_{sat} - P_a)}{Q/A} [\text{m}^2 \text{Pa/W}] \quad \text{Eq 3.}$$

$$i_m = \frac{60.6515 \cdot R_t}{R_{et}} \quad \text{Eq 4.}$$

Ensembles

Twenty-two different ensemble configurations were tested as they would be worn. Full descriptions of each of the test configurations is outlined in Table 1; while associated photographs of ensemble components are provided in Appendix A.

Table 1. Ensemble descriptions

| Ensemble | | Description |
|-----------------|--|--|
| US 1 | US Army | US Army - Silk-weight undershirt and drawers; Mid-weight shirt and drawers |
| US 2 | | US Army - Silk-weight undershirt and drawers; Mid-weight shirt and drawers; Fleece Jacket |
| US 3 | | US Army - Silk-weight undershirt and drawers; Mid-weight shirt and drawers; Fleece Jacket; Soft Shell jacket and trousers |
| US 4 | | US Army - Silk-weight undershirt and drawers; Mid-weight shirt and drawers; Fleece Jacket; Soft Shell jacket and trousers; Extreme Cold Weather (ECW) Parka and trousers |
| US 5 | | US Army - Mid-weight shirt and drawers; Soft Shell jacket and trousers |
| US 6 | | US Army - Mid-weight shirt and drawers; Soft Shell jacket and trousers; Extreme Cold Weather (ECW) Parka and trousers |
| US 7 | | US Army - Silk-weight undershirt and drawers; Wind jacket; Soft Shell trousers |
| US 8 | | US Army - Silk-weight undershirt and drawers; Soft Shell jacket and trousers |
| US 9 | | US Army - Silk-weight undershirt and drawers; Extreme Cold Weather (ECW) jacket and trousers |
| CA 1 | Canadian Department of National Defence | Canadian - Thermal undershirt and Long Johns; CADPAT ICE jacket and trousers |
| CA 2 | | Canadian - Thermal undershirt and Long Johns; CADPAT IECS Parka – HOOD DOWN; CADPAT IECS Bib pants |
| CA 3 | | Canadian - Thermal undershirt and Long Johns; CADPAT IECS Parka – HOOD UP; CADPAT IECS Bib pants |
| CA 4 | | Canadian - Thermal undershirt and Long Johns; CADPAT Fleece jacket and trousers; CADPAT IECS Parka - HOOD DOWN; CADPAT IECS Bib pants |
| CA 5 | | Canadian - Thermal undershirt and Long Johns; CADPAT Fleece jacket and trousers; CADPAT IECS Parka - HOOD UP; CADPAT IECS Bib pants |
| CA 6 | | Canadian - Thermal undershirt and Long Johns; CADPAT Fleece jacket and trousers; CADPAT IECS Bib pants; Canada Goose Snow Mantra Winter parka |
| CA 7 | | Canadian - Thermal undershirt and Long Johns; CADPAT Fleece jacket and trousers; CADPAT ICE jacket and trousers |
| CA 8 | | Canadian - Thermal undershirt and Long Johns; CADPAT Fleece jacket and trousers; CADPAT IECS Bib pants; Canada Goose Snow Mantra Winter parka |
| N 1 | Norwegian military | Norwegian - Mesh underwear; wool terry cloth underwear; GORE-Tex® jacket and pants; white camouflage jacket and pants; hood down |
| N 2 | | Norwegian - Mesh underwear; wool terry cloth underwear; Cotton Field Shirt; GORE-Tex® jacket and pants; hood down |
| N 3 | | Norwegian - Mesh underwear; wool terry cloth underwear; Cotton Field Shirt; White Camouflage jacket and pants; hood down |
| N 4 | | Norwegian - Mesh underwear; wool terry cloth underwear; Cotton Field Shirt; Cold Weather jacket and pants |
| N 5 | | Norwegian - Mesh underwear; wool terry cloth underwear; Cotton Field Shirt; White Camouflage Uniform; Cold Weather jacket and pants |

Insulation Required

A simple calculation based on the International Organization Standardization (ISO) technical report (ISO 11079) [33], was used as an evaluation metric of the insulation required (IREQ) for given environments and activities to compare ensemble performance. The IREQ method functionally describes the concept for balancing the heat exchange between the human and the environment, simplified as:

$$M - W = E_{res} + C_{res} + E + K + R + C + S \quad \text{Eq 5.}$$

where M is metabolic heat produced, W is effective mechanical work and collectively M-W represents the heat produced within the human; while the opposite side of this balance, E_{res} and C_{res} represent the respiratory heat exchange (evaporative and convective), and E, K, R, and C represent the conventional heat exchange methods (evaporative, conductive, radiative, and convective) and S is heat storage.

The IREQ equation (Eqs. 6 and 7), outlines the rational balance of these methods to include a thermal insulation via clothing elements needed to maintain this balance, seen simply as:

$$IREQ = \frac{\bar{t}_{sk} - t_{cl}}{R + C} \quad \text{Eq 6.}$$

more formally as:


$$IREQ = \frac{\bar{t}_{sk} - t_{cl}}{M - W - E_{res} - C_{res} - E} \quad \text{Eq 7.}$$

where t_{sk} is mean skin temperature, t_{cl} clothing surface temperature, and $M - W - E_{res} - C_{res} - E = R + C$

The insulation required minimum and neutral (IREQ_{min} and IREQ_{neutral}) were used to calculate the minimal and ideal amounts of insulation needed to maintain thermal balance (minimum) and to maintain an equilibrium balance (neutral).

The ISO 11079 helpfully outlines a general scenario for the minimum required insulation (IREQ_{min}) for multiple work intensities and environments (Figure 3). From Figure 3, we can see that in low air velocity conditions (still air; 0.2m/s) and relative humidity (RH) of 50% that the range of required clothing insulation for an individual slightly above resting (70 W/m²) in 10 to -50 °C is 1.8 to 8.5 clo. Intuitively, as work rate intensifies to higher levels, this range shifts downward relative to environment.

Figure 3. Outline of minimum insulation required ($IREQ_{min}$) for various environmental conditions and work intensities [33]

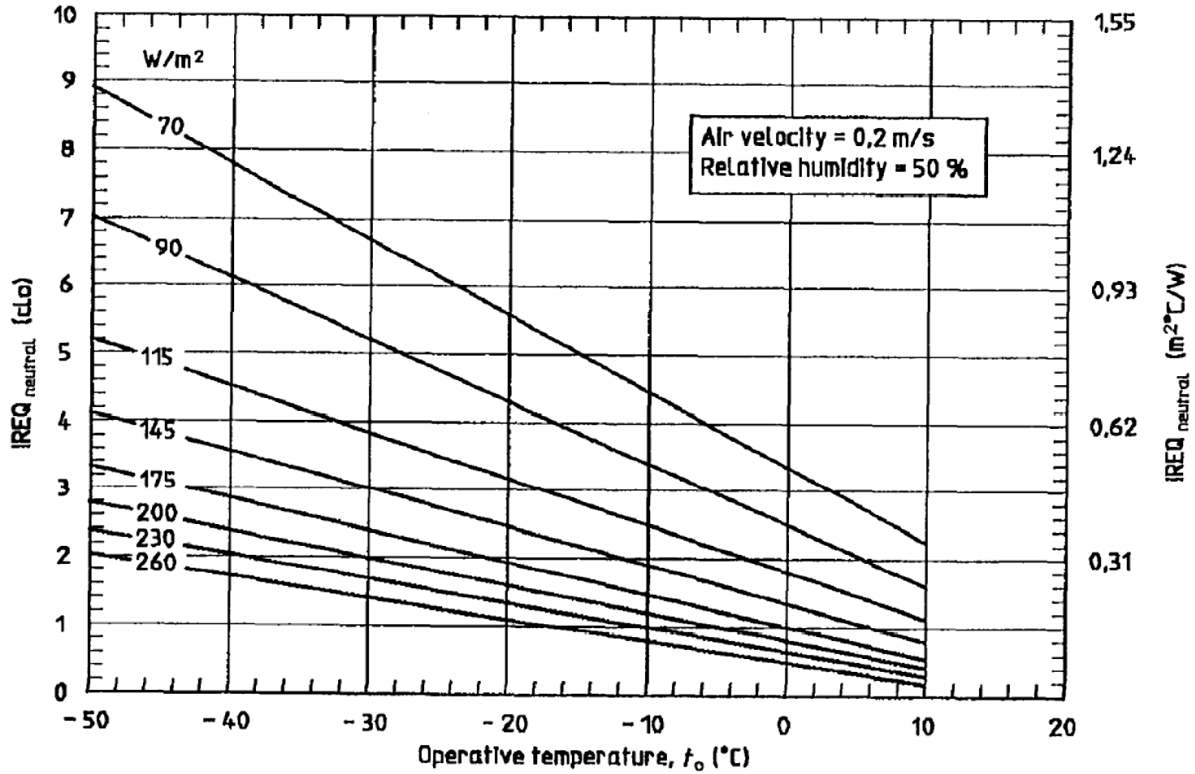


Duration Limited Exposure (DLE)

Along with the IREQ method, ISO 11079 [33] also outlines the calculation for a duration limited exposure (DLE) for estimating a maximal safe exposure time to a given environment and associated work intensity, in the event the insulation provided is insufficient (i.e., below the estimated IREQ). The DLE is the balance of the limits of body heat content (Q_{lim}) divided by the body heat storage (S), seen as:

$$DLE = \frac{Q_{lim}}{S}$$

The ISO 11079 has also outlined a general scenario for the DLE, in hours, at a working activity rate of $115 W/m^2$ (~2 METS) for different clothing insulation values (1, 2, 3, and 4 clo) within various environments (Figure 4). For example, Figure 4 shows that in a clothing ensemble with insulation of 2 clo, working at 2 METS, in $-20^\circ C$ conditions, that an individual should limit their exposure to no more than ~30 minutes (Figure 4; ref point A).

Figure 4. Outline of duration limited exposure (DLE) across cold environments for 4 levels of total clothing insulation (clo) at one work intensity [33]

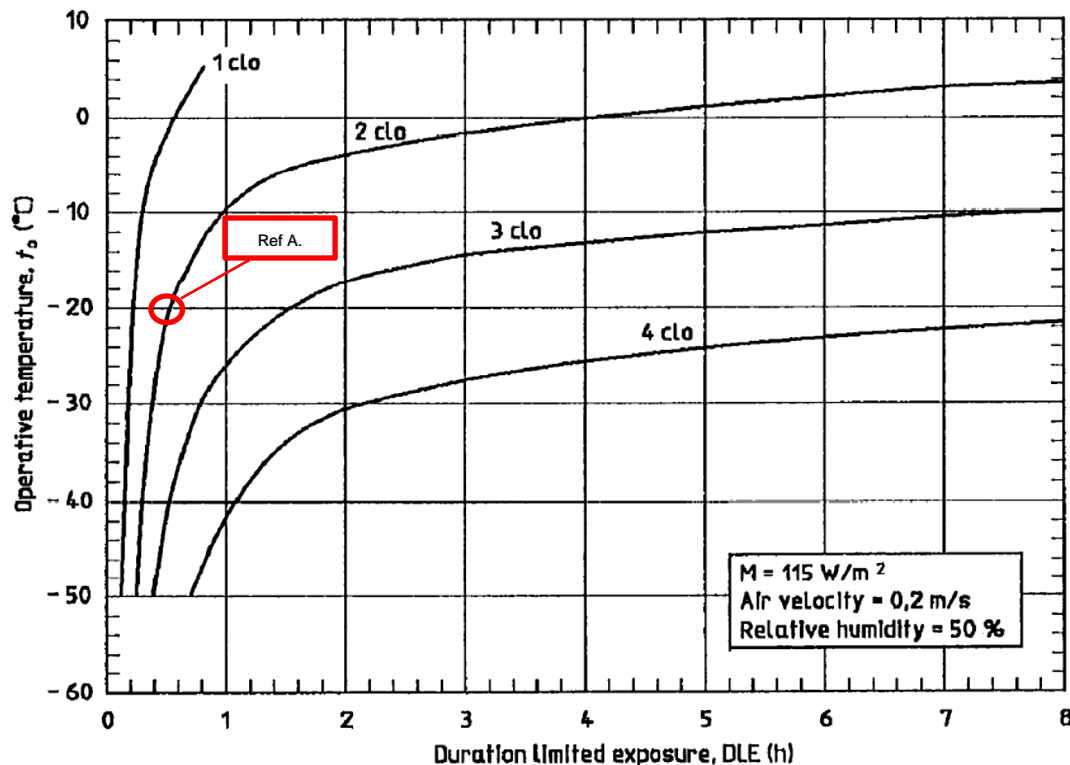

Heat stress

Dynamic activities of military service members and increasing levels of insulation, can reduce the risk of cold exposure injuries but as a consequence can impose a level of heat stress on an individual. To outline the contrast of this and provide an indication of higher risks of sweating, complimentary heat stress modeling of each of these ensembles was conducted using a single, temperate environmental condition, and a single high work intensity rate to show implications of the potential for thermal strain. This modeling was conducted using the heat strain decision aid (HSDA) [34]. This biophysics-based model takes into account inputs of individual, clothing, activity, and environment and translates them to core temperature rise over time. Estimated values for the effects of wind velocity on these properties was used to provide inputs to this model [35].

RESULTS

Biophysical Results

Simple descriptive statistics were done for the total, and for each country independently. Total measured biophysical values (mean \pm SD; min-max) for the 22 ensembles were: R_t : 0.312 ± 0.083 ; 0.201-0.482, clo: 2.011 ± 0.533 ; 1.296-3.109, R_{et} :


46.831 \pm 11.431; 23.5-67.77, i_m : 0.407 \pm 0.062; 0.313-0.549, i_m/clo : 0.215 \pm 0.064; 0.139-0.4. US Army ensembles: R_t : 0.257 \pm 0.072; 0.201-0.435, clo : 1.656 \pm 0.468; 1.296-2.806, R_{et} : 40.552 \pm 12.969; 23.5-67.77, i_m : 0.397 \pm 0.082; 0.313-0.549, i_m/clo : 0.253 \pm 0.081; 0.139-0.4. Canadian ensembles: R_t : 0.380 \pm 0.06; 0.281-0.482, clo : 2.45 \pm 0.389; 1.812-3.109, R_{et} : 51.888 \pm 7.067; 42.72-63.55, i_m : 0.443 \pm 0.029; 0.399-0.494, i_m/clo : 0.184 \pm 0.025; 0.148-0.22. Norwegian ensembles: R_t : 0.302 \pm 0.053; 0.254-0.373, clo : 1.945 \pm 0.341; 1.638-2.406, R_{et} : 50.044 \pm 10.460; 38.53-63.91, i_m : 0.368 \pm 0.022; 0.354-0.408, i_m/clo : 0.194 \pm 0.040; 0.147-0.244.

A graphical representation of the clo and i_m/clo for the 22 ensembles is shown in Figure 5; while the corresponding data is shown in Table 2. From Figure 5 a general trend of higher insulation relating to lower permeability (e.g., i_m/clo) can be observed. This indicates the need for well-defined tradeoff assessment for clothing usage based on anticipated activities and environments, i.e., high insulation protects from the cold; while related low permeability increases risk for thermal strain. This balance is specifically important when considering the added risk resulting from sweating in the cold (i.e., sweat freezes and increases risk of cold injuries).

Table 2. Biophysical measures for each ensemble


| Ensemble | Thermal Resistance (R_t ; m ² K/W) | Thermal Insulation (clo) | Evaporative Resistance (R_{et} ; m ² Pa/W) | Permeability Index (i_m) | Evaporative Potential (i_m/clo) |
|----------|---|---------------------------------|---|---------------------------------|--|
| US 1 | 0.201 | 1.296 | 23.50 | 0.519 | 0.400 |
| US 2 | 0.240 | 1.548 | 26.53 | 0.549 | 0.354 |
| US 3 | 0.268 | 1.729 | 44.98 | 0.361 | 0.209 |
| US 4 | 0.435 | 2.806 | 67.77 | 0.389 | 0.139 |
| US 5 | 0.231 | 1.490 | 43.19 | 0.324 | 0.218 |
| US 6 | 0.283 | 1.825 | 46.71 | 0.367 | 0.201 |
| US 7 | 0.208 | 1.342 | 40.36 | 0.313 | 0.233 |
| US 8 | 0.204 | 1.316 | 33.64 | 0.368 | 0.280 |
| US 9 | 0.241 | 1.554 | 38.29 | 0.382 | 0.246 |
| CA 1 | 0.281 | 1.812 | 42.72 | 0.399 | 0.220 |
| CA 2 | 0.326 | 2.103 | 44.01 | 0.449 | 0.214 |
| CA 3 | 0.379 | 2.445 | 55.36 | 0.415 | 0.170 |
| CA 4 | 0.361 | 2.328 | 47.79 | 0.458 | 0.197 |
| CA 5 | 0.412 | 2.657 | 57.55 | 0.434 | 0.163 |
| CA 6 | 0.482 | 3.109 | 63.55 | 0.460 | 0.148 |
| CA 7 | 0.409 | 2.638 | 50.26 | 0.494 | 0.187 |
| CA 8 | 0.389 | 2.509 | 53.86 | 0.438 | 0.175 |
| N 1 | 0.281 | 1.812 | 47.210 | 0.361 | 0.199 |
| N 2 | 0.254 | 1.638 | 43.050 | 0.358 | 0.218 |
| N 3 | 0.259 | 1.671 | 38.530 | 0.408 | 0.244 |
| N 4 | 0.341 | 2.199 | 57.520 | 0.360 | 0.163 |
| N 5 | 0.373 | 2.406 | 63.910 | 0.354 | 0.147 |

Figure 5. Thermal insulation (clo) and evaporative potential (im/clo) for each ensemble

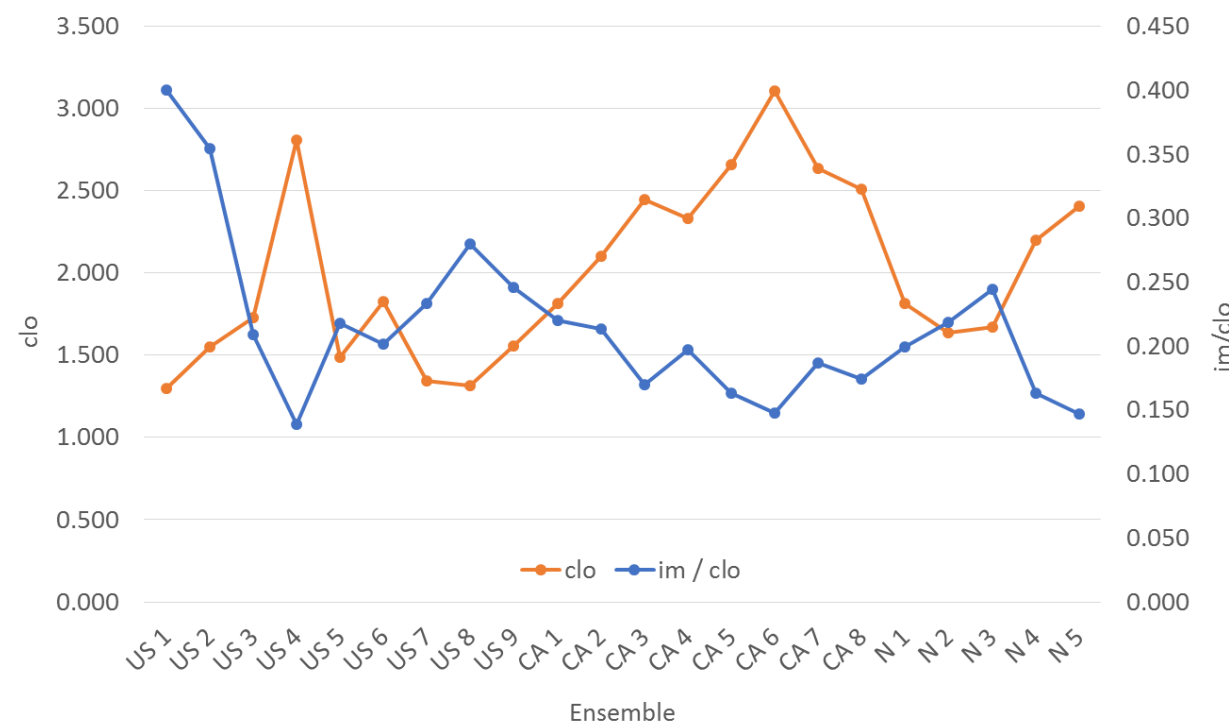


Ranking by level of thermal insulation (clo) is shown graphically in Figure 6. As can be seen the Canadian CA6 and US Army ensemble US 4 provide the highest level of thermal insulation. This higher value indicates higher protection from extreme cold weather extremes based on low activity or resting conditions.

Figure 6. Ranking of clothing ensembles based on thermal insulation (clo)

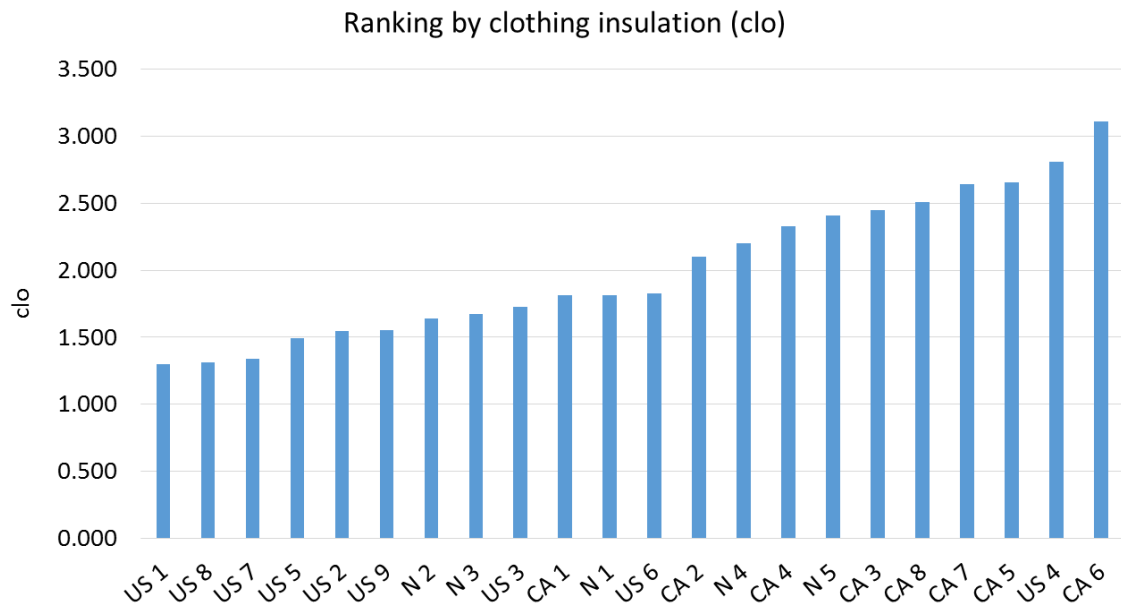

In contrast to levels of thermal insulation (clo), Figure 7 shows a ranking of clothing ensembles based on evaporative potential (i_m/clo). As can be seen the US Army ensembles, US 1 and US 2 provide the highest evaporative potential (i_m/clo) values, indicating reduced likelihood of imposed heat strain.

Figure 7. Ranking of clothing ensembles based on evaporative potential (i_m/clo)

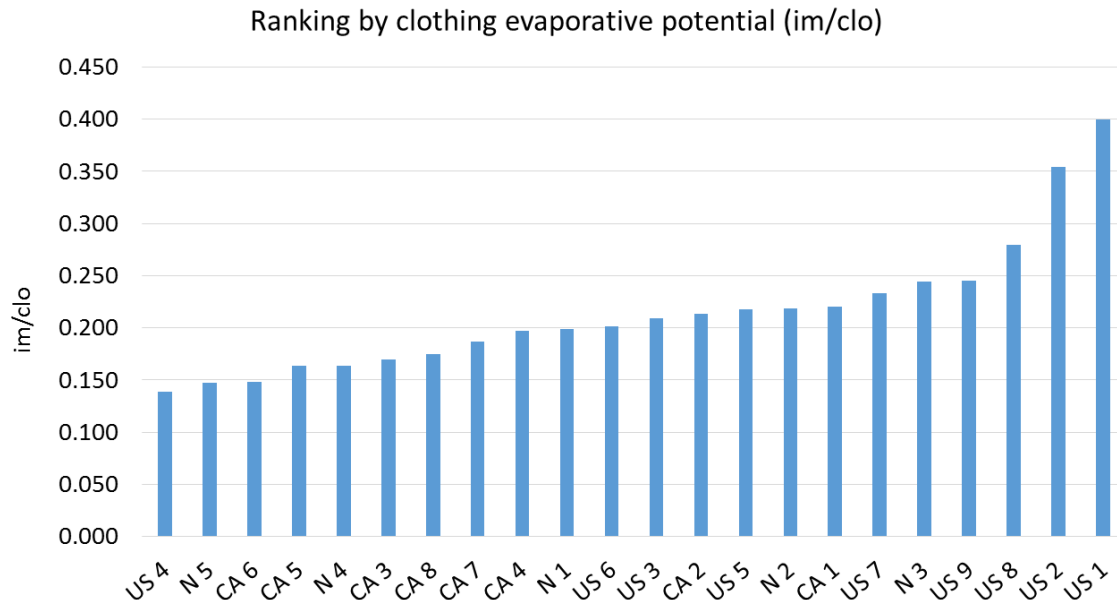

Insulation Required

Comparisons of calculated insulation required minimal (in three environmental conditions at both resting (58.2 W/m^2) and 2 METs activity (116 W/m^2) is shown in Table 3.

Table 3. Calculated Insulation Required by Environment: resting and moderate activity

| Environment | Activity Rate | Insulation Minimum Required (IREQ _{min}) - clo | Insulation Required for Neutral Response (IREQ _{neutral}) – clo |
|-----------------------------------|---|--|---|
| -10°C, 50%RH, still air | Resting (58.2 W/m^2) 1 MET | 5.1 | 5.5 |
| -10°C, 50%RH, still air + 0.3 m/s | Resting (116 W/m^2) 2 MET | 2.2 | 2.5 |
| -20°C, 50%RH, still air | Resting (58.2 W/m^2) 1 MET | 6.4 | 6.8 |
| -20°C, 50%RH, still air + 0.3 m/s | Resting (116 W/m^2) 2 MET | 2.9 | 3.2 |
| -30°C, 50%RH, still air | Resting (58.2 W/m^2) 1 MET | 7.8 | 8.1 |
| -30°C, 50%RH, still air + 0.3 m/s | Resting (116 W/m^2) 2 MET | 3.5 | 3.9 |

Comparisons of clothing insulation values in Table 2 and estimations of the required insulation in Table 3 show deficiencies and where clothing ensembles meet the guidance values. Table 4 shows where each ensemble meets or doesn't meet the standards outlined for resting and moderate activity in three environments. Table 4 and Figure 8 clearly show that within these three environments (-10, -20, and -30°C) that none of the ensembles meets the minimum required insulation for resting. Table 4 and Figure 9 show that none of the ensembles meet the required insulation for moderate (2 MET) work in -30°C conditions; while only one ensemble (CA 6) meets the neutral (IREQneutral) criteria for -20°C conditions. However, from Table 4 and Figure 9 we see that at a moderate (2 MET) work rate several ensembles meet the minimal or neutral (IREQmin; IREQneutral) values for -10°C conditions

Table 4. Ensemble comparison to guidance requirements for resting and moderate activity in three environmental conditions

| | 1 MET and -10°C | 2 MET and -10°C | 1 MET and -20°C | 2 MET and -20°C | 1 MET and -30°C | 2 MET and -30°C |
|-------------|-----------------|-----------------|-----------------|-----------------|-----------------|-----------------|
| IREQmin | 5.1 | 2.2 | 6.4 | 2.9 | 7.8 | 3.5 |
| IREQneutral | 5.5 | 2.5 | 6.8 | 3.2 | 8.1 | 3.9 |
| US 1 | 1.3 | 1.3 | 1.3 | 1.3 | 1.3 | 1.3 |
| US 2 | 1.5 | 1.5 | 1.5 | 1.5 | 1.5 | 1.5 |
| US 3 | 1.7 | 1.7 | 1.7 | 1.7 | 1.7 | 1.7 |
| US 4 | 2.8 | 2.8 | 2.8 | 2.8 | 2.8 | 2.8 |
| US 5 | 1.5 | 1.5 | 1.5 | 1.5 | 1.5 | 1.5 |
| US 6 | 1.8 | 1.8 | 1.8 | 1.8 | 1.8 | 1.8 |
| US 7 | 1.3 | 1.3 | 1.3 | 1.3 | 1.3 | 1.3 |
| US 8 | 1.3 | 1.3 | 1.3 | 1.3 | 1.3 | 1.3 |
| US 9 | 1.6 | 1.6 | 1.6 | 1.6 | 1.6 | 1.6 |
| CA 1 | 1.8 | 1.8 | 1.8 | 1.8 | 1.8 | 1.8 |
| CA 2 | 2.1 | 2.1 | 2.1 | 2.1 | 2.1 | 2.1 |
| CA 3 | 2.4 | 2.4 | 2.4 | 2.4 | 2.4 | 2.4 |
| CA 4 | 2.3 | 2.3 | 2.3 | 2.3 | 2.3 | 2.3 |
| CA 5 | 2.7 | 2.7 | 2.7 | 2.7 | 2.7 | 2.7 |
| CA 6 | 3.1 | 3.1 | 3.1 | 3.1 | 3.1 | 3.1 |
| CA 7 | 2.6 | 2.6 | 2.6 | 2.6 | 2.6 | 2.6 |
| CA 8 | 2.5 | 2.5 | 2.5 | 2.5 | 2.5 | 2.5 |
| N 1 | 1.8 | 1.8 | 1.8 | 1.8 | 1.8 | 1.8 |
| N 2 | 1.6 | 1.6 | 1.6 | 1.6 | 1.6 | 1.6 |
| N 3 | 1.7 | 1.7 | 1.7 | 1.7 | 1.7 | 1.7 |
| N 4 | 2.2 | 2.2 | 2.2 | 2.2 | 2.2 | 2.2 |
| N 5 | 2.4 | 2.4 | 2.4 | 2.4 | 2.4 | 2.4 |

Figure 8. Compared insulation (clo) values to guidance required (IREQmin and IREQneutral) for three environments during rest.


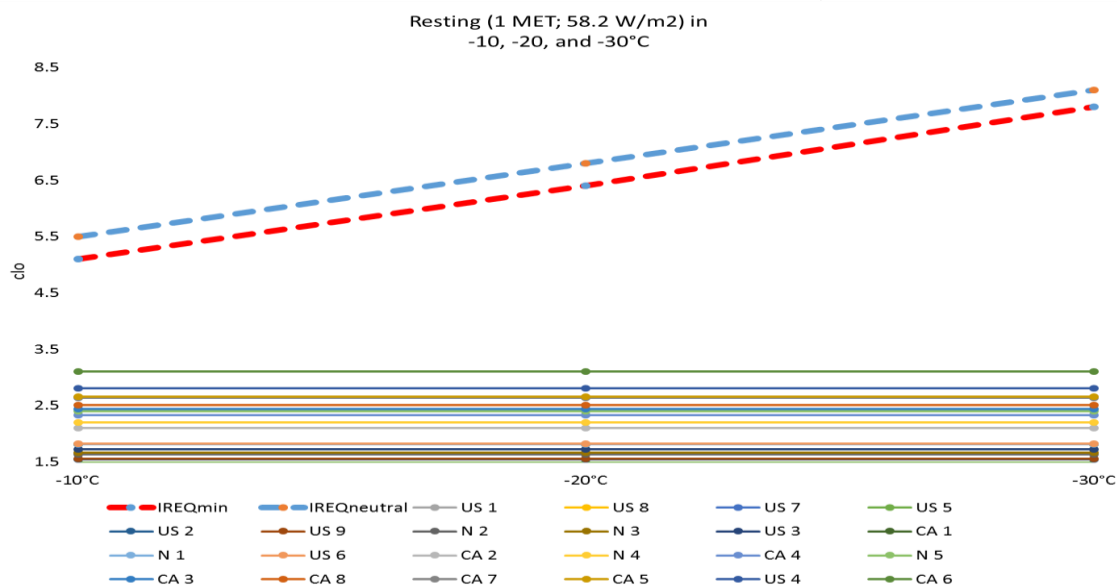


Figure 9. Compared insulation (clo) values to guidance required (IREQmin and IREQneutral) for three environments during moderate activity (2 MET).

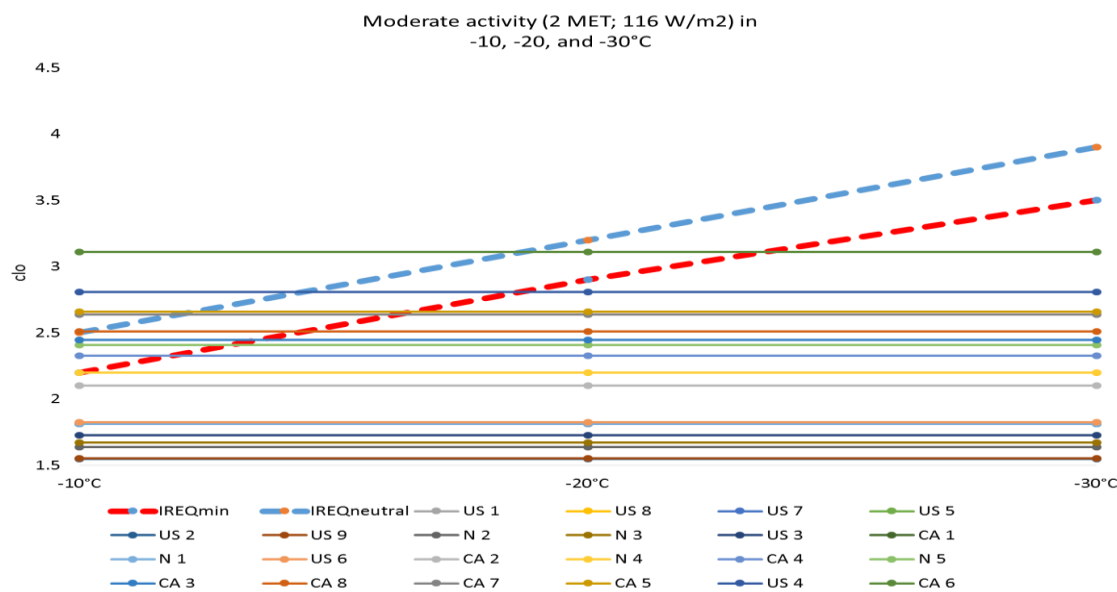


Duration Limited Exposure (DLE)

Comparisons of calculated duration limited exposure times (hours) in three environmental conditions at both resting (58.2 W/m²) and 2 METs activity (116 W/m²) is shown in both Table 5 and in Figure 10.

Table 5. Duration limited exposure (DLE) by ensemble for three environments (-10, -20, and -30°C during rest and moderate activity (2 MET)

| | -10°C Rest | | -10°C 2 MET | | -20°C Rest | | -20°C 2 MET | | -30°C Rest | | -30°C 2 MET | |
|----------|------------|--------|-------------|--------|------------|--------|-------------|--------|------------|--------|-------------|--------|
| Ensemble | DLEmin | DLEneu | DLEmin | DLEneu | DLEmin | DLEneu | DLEmin | DLEneu | DLEmin | DLEneu | DLEmin | DLEneu |
| US 1 | 0.4 | 0.3 | 0.7 | 0.5 | 0.2 | 0.2 | 0.4 | 0.3 | 0.2 | 0.2 | 0.3 | 0.2 |
| US 8 | 0.4 | 0.3 | 0.7 | 0.5 | 0.2 | 0.2 | 0.4 | 0.3 | 0.2 | 0.2 | 0.3 | 0.2 |
| US 7 | 0.4 | 0.3 | 0.7 | 0.5 | 0.2 | 0.2 | 0.4 | 0.3 | 0.2 | 0.2 | 0.3 | 0.2 |
| US 5 | 0.4 | 0.4 | 0.9 | 0.6 | 0.3 | 0.3 | 0.5 | 0.4 | 0.2 | 0.2 | 0.3 | 0.3 |
| US 2 | 0.4 | 0.4 | 0.9 | 0.6 | 0.3 | 0.3 | 0.5 | 0.4 | 0.2 | 0.2 | 0.3 | 0.3 |
| US 9 | 0.4 | 0.4 | 1.1 | 0.7 | 0.3 | 0.3 | 0.6 | 0.4 | 0.3 | 0.2 | 0.4 | 0.3 |
| N 2 | 0.4 | 0.4 | 1.1 | 0.7 | 0.3 | 0.3 | 0.6 | 0.4 | 0.3 | 0.2 | 0.4 | 0.3 |
| N 3 | 0.5 | 0.4 | 1.3 | 0.8 | 0.3 | 0.3 | 0.6 | 0.5 | 0.3 | 0.3 | 0.4 | 0.3 |
| US 3 | 0.5 | 0.4 | 1.3 | 0.8 | 0.3 | 0.3 | 0.6 | 0.5 | 0.3 | 0.3 | 0.4 | 0.3 |
| CA 1 | 0.5 | 0.5 | 1.6 | 1 | 0.3 | 0.3 | 0.7 | 0.5 | 0.3 | 0.3 | 0.4 | 0.4 |
| N 1 | 0.5 | 0.5 | 1.6 | 1 | 0.3 | 0.3 | 0.7 | 0.5 | 0.3 | 0.3 | 0.4 | 0.4 |
| US 6 | 0.5 | 0.5 | 1.6 | 1 | 0.3 | 0.3 | 0.7 | 0.5 | 0.3 | 0.3 | 0.4 | 0.4 |
| CA 2 | 0.6 | 0.6 | 3.8 | 1.6 | 0.4 | 0.4 | 1 | 0.7 | 0.3 | 0.3 | 0.6 | 0.5 |
| N 4 | 0.7 | 0.6 | 8 | 2 | 0.4 | 0.4 | 1.2 | 0.8 | 0.4 | 0.3 | 0.6 | 0.5 |
| CA 4 | 0.7 | 0.6 | 8 | 2.5 | 0.5 | 0.4 | 1.4 | 0.9 | 0.4 | 0.4 | 0.7 | 0.6 |
| N 5 | 0.8 | 0.7 | 8 | 3.4 | 0.5 | 0.4 | 1.6 | 1.1 | 0.4 | 0.4 | 0.8 | 0.6 |
| CA 3 | 0.8 | 0.7 | 8 | 3.4 | 0.5 | 0.4 | 1.6 | 1.1 | 0.4 | 0.4 | 0.8 | 0.6 |
| CA 8 | 0.8 | 0.7 | 8 | 8 | 0.5 | 0.5 | 1.9 | 1.2 | 0.4 | 0.4 | 0.9 | 0.7 |
| CA 7 | 0.9 | 0.8 | 8 | 8 | 0.5 | 0.5 | 2.4 | 1.4 | 0.4 | 0.4 | 1 | 0.8 |
| CA 5 | 0.9 | 0.8 | 8 | 8 | 0.6 | 0.5 | 3.1 | 1.6 | 0.5 | 0.4 | 1.1 | 0.8 |
| US 4 | 1 | 0.9 | 8 | 8 | 0.6 | 0.5 | 4.2 | 1.9 | 0.5 | 0.5 | 1.2 | 0.9 |
| CA 6 | 1.3 | 1.1 | 8 | 8 | 0.7 | 0.6 | 8 | 3.8 | 0.6 | 0.5 | 1.9 | 1.3 |


Figure 10. Duration limited exposure (DLE) (hours) by ensemble for three environments (-10, -20, and -30°C during rest and moderate activity (2 MET)

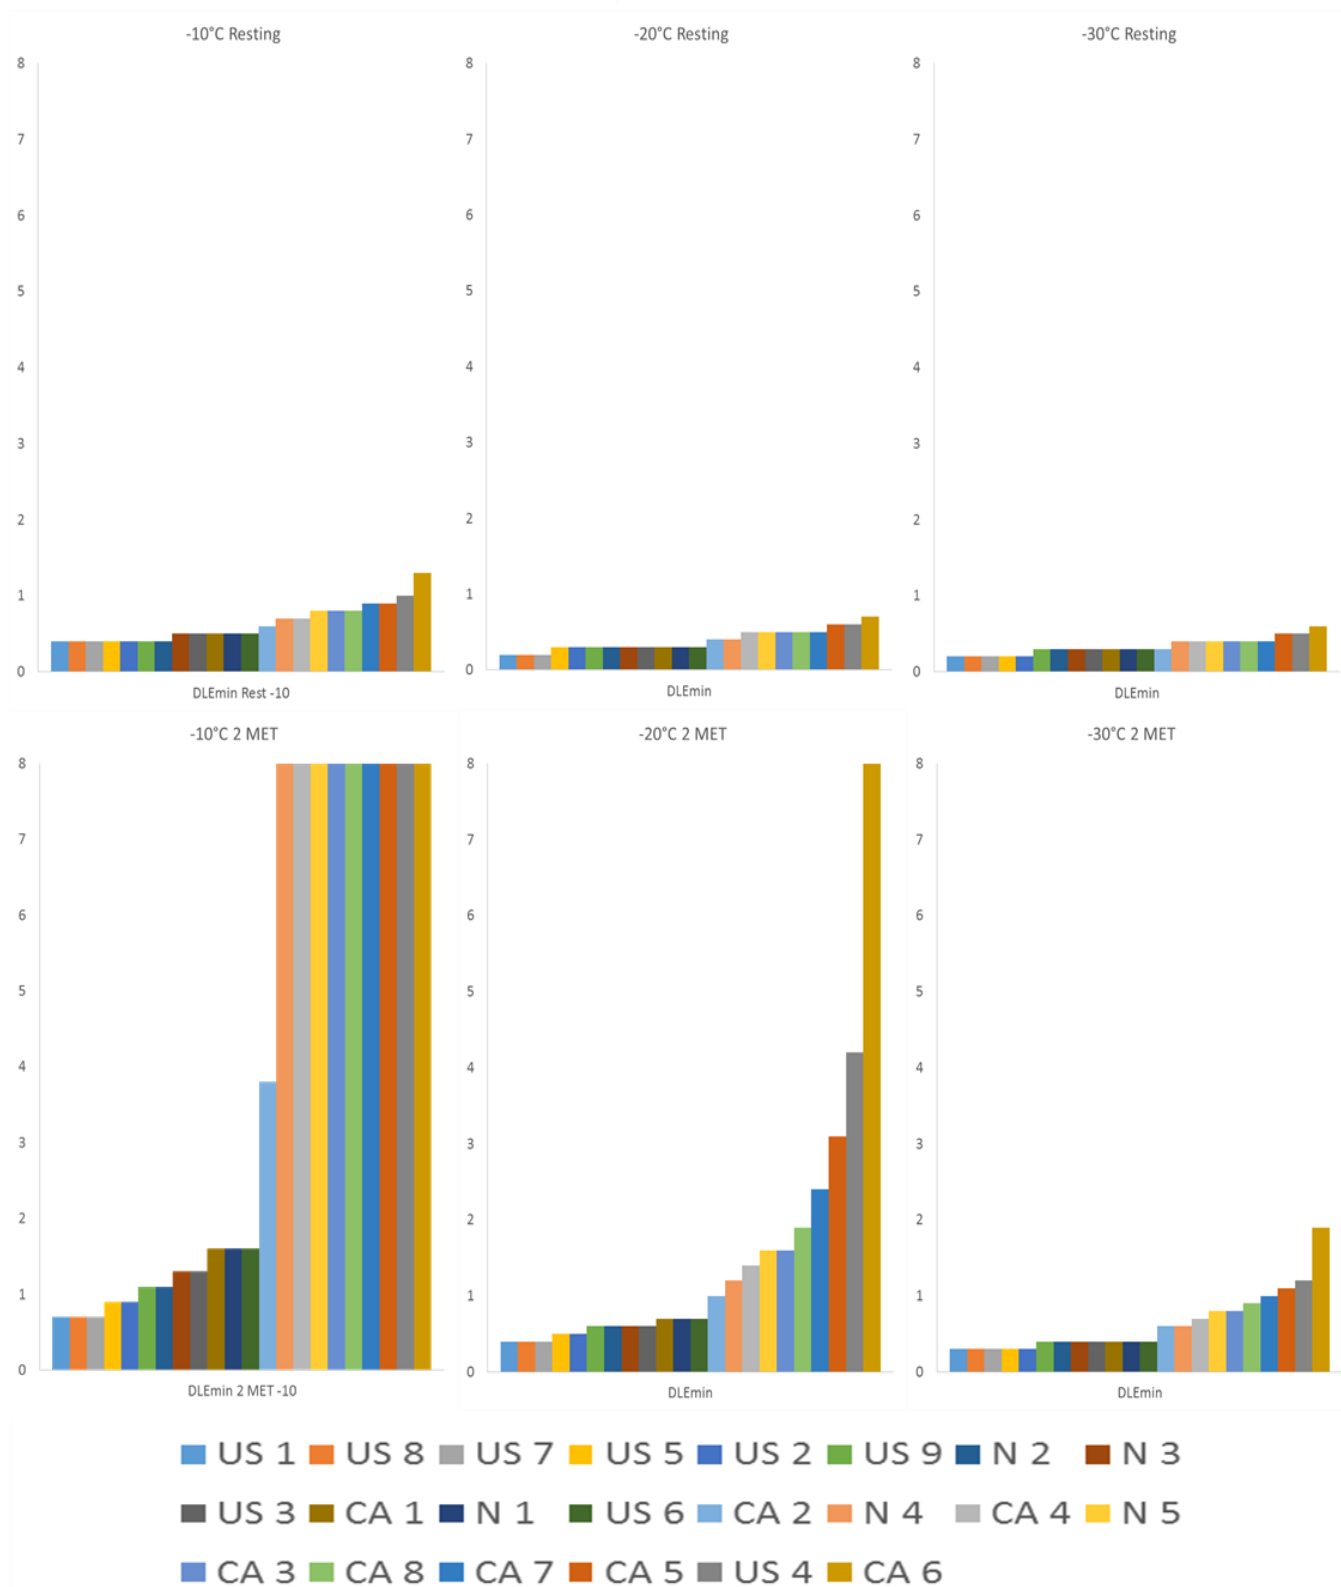

Heat stress

Comparisons of modeled heat stress in one cold environmental condition and moderate work rate (191 W/m^2) showed the noticeable differences over a two hour period across uniforms. At the two hour mark, an absolute difference of 0.85°C could be observed between the least (US 1) and most (US 4) thermally burdensome uniforms, with a standard deviation of 0.24 across all ensembles (Figure 8).

Figure 11. Compared heat stress over a 120 minutes in a cold environment (10°C) at a moderate work rate (191 W/m^2)

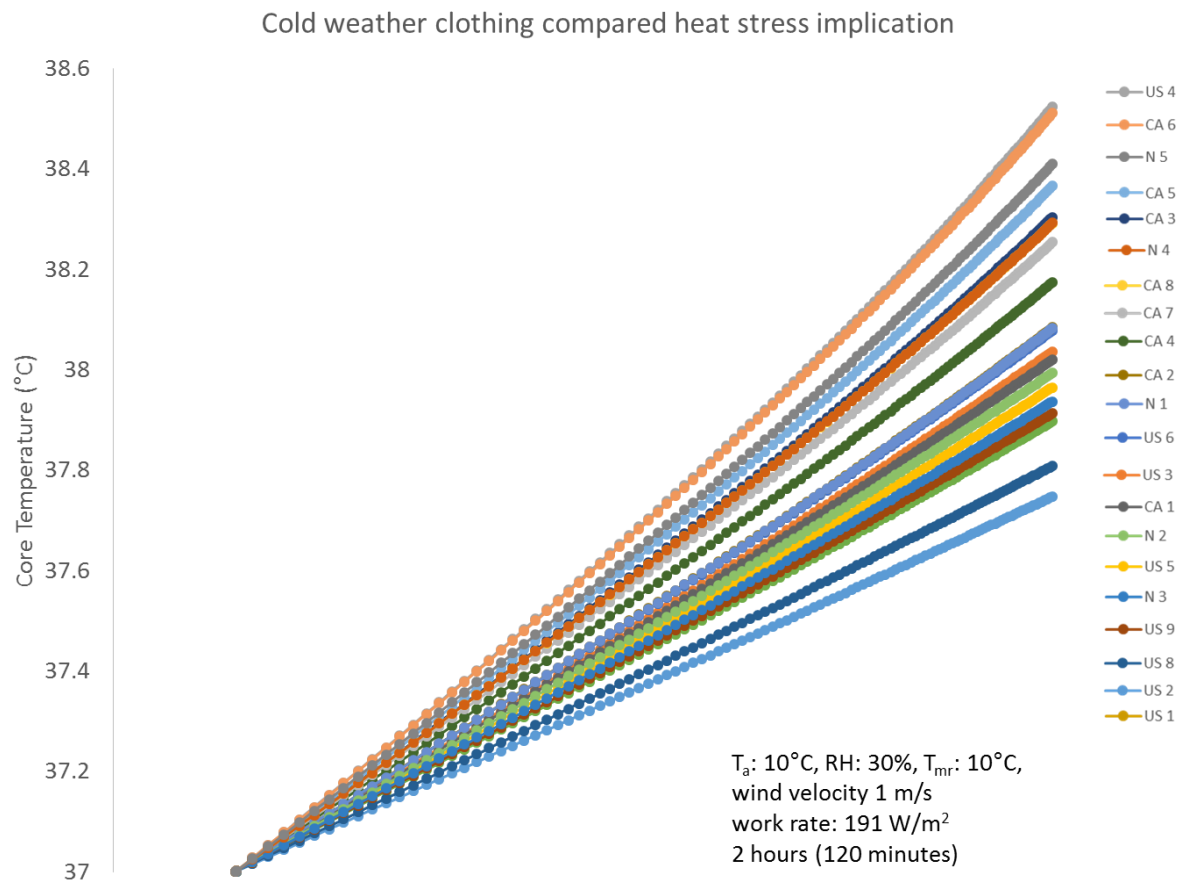


DISCUSSION

This study compared the biophysical characteristics of 22 cold weather ensembles using standard test methods and compared their performance using multiple modeling methods. This combination of testing and simple analytical assessment can prove as a meaningful step in the evaluation of clothing systems. However, it is important to note that more sophisticated modeling methods and human testing should be used for more comprehensive analyses. More complex physiological models such as the six cylinder thermoregulatory model (SCTM) from Xu and Werner [36], provide the added benefit of being rationally based and accounting for physiological responses in more detail (metabolism, vasomotor control, sweat production, and blood pooling) versus the simple heat balance methods of the IREQ [33].

The methods outlined in this report use the current minimal amount of testing that allows for modeling of human-level scenarios. From a time and cost perspective it is important to use all of the available methods to ensure both quantitative steps toward improvements as well as efficient and effective use of resources. Umbach [37] outlined a five level approach for clothing development and assessing the heat transfer properties of textiles; a simplified version of this is recreated in Figure 12 with a third level of biomedical modeling added, rather than a side process. Cost, time, and resources required increases with each level of assessment. At the lowest level of *physical analysis* (level 1), for example, clothing can be weighed and inspected for physical attributes. *Biophysical analysis* (level 2), which typically involves measurement of heat transfer properties, can be done using sweating guarded hotplate (SGHP) measurements followed by subsystem and full ensemble level assessments, each requiring specialized test equipment, facilities, and technicians. *Biomedical modeling* (level 3) can be used to predict thermo-physiological impacts from the heat transfer properties of clothing, requiring expertise and time to perform specialized analyses. These first three levels require equipment and skills; however, they do not require the time, expense, and complexity of human subject research.

The traditional lowest level of human use research, *controlled lab evaluations* (level 4) requires specialized equipment and test facilities which not only increase costs but increase the supporting staff needed, broad expertise including physiology, and the added resources demand of studying human research volunteers (~8-20). *Controlled field evaluation* (level 5) may be more complex than level 4, with increases in cost, logistical complexity, and resources associated with the additional oversight required in a less contained environment, and typically an increase in the number of human research volunteers (20+), as well as a broader level of expertise (e.g., specialized understanding of activities being conducted). Once these controlled studies have been conducted, moving towards *field evaluations* (level 6) would include a much larger, more inclusive set of human research volunteers, seen more as customers or end users at this point, reflecting the targeted end user population.

Figure 12. Levels of clothing system testing

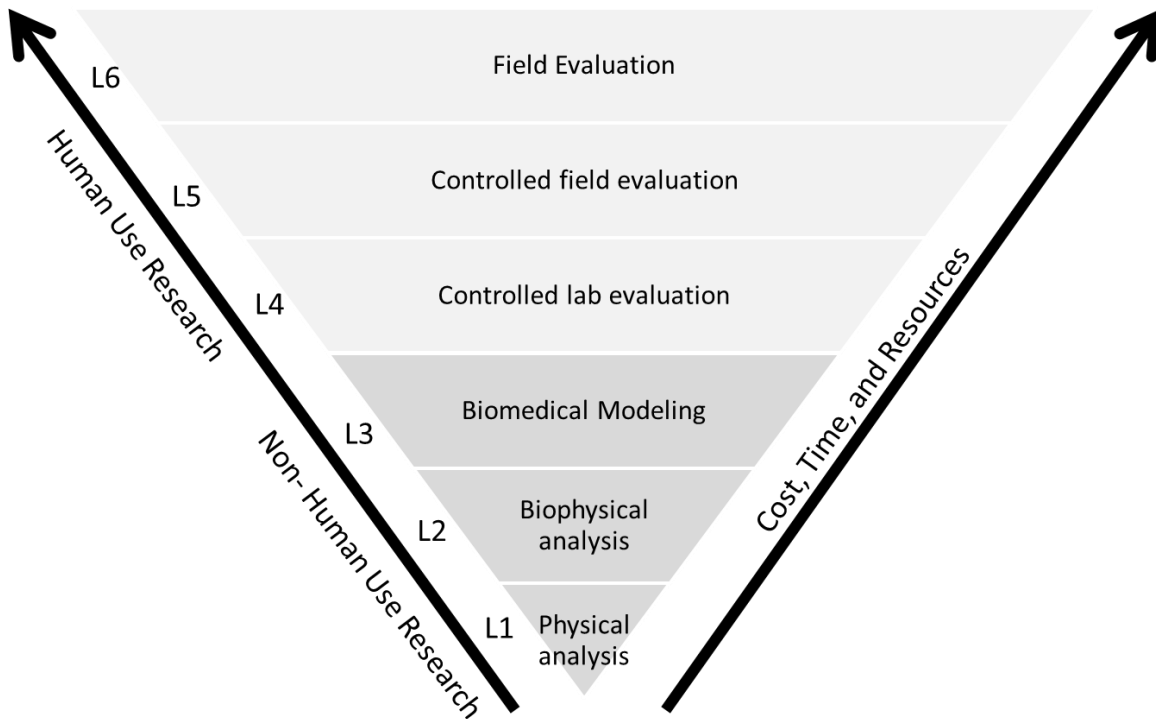

Assessing 2-dimensional swatches, textiles of single or multiple layered materials, can be done using a SGHP in accordance with ISO 11092 [38-39]. This method simulates the heat transfer of the human skin through the material tested into a controlled environment. While this method is a quick and cost effective means of evaluating textile materials, the resulting data often does not correspond to that of full ensembles. The main reason for this lack of correspondence is the fact that SGHP lacks the air gaps between the skin and the base layer, and between clothing layers that are present when 3-dimensional garments of varied form and fit are tested on the manikins. Xu et al., [40] outlines the critical importance of understanding the air boundary layers ('air gap') between clothing layers. Testing with thermal manikins allows for an inclusive system-level testing of the total resistances (thermal and evaporative) of an ensemble; while the total resistance of any ensemble consists of three main elements: air gap (R_{gap}), clothing textile (R_{cl}), and boundary layer (R_{bl}); where the total is seen as: $Resistance = R_{gap} + R_{cl} + R_{bl}$. While work has been done to estimate the air gap layers [41-43], more work is needed for an open-access standard (e.g., ISO, ASTM).

REFERENCES

1. Carter III R, Cheuvront SN, Williams JO, Kolka MA, Stephenson LA, Sawka MN, & Amoroso PJ. Epidemiology of Hospitalizations and Deaths from Heat Illness in Soldiers. *Medicine & Science in Sports & Exercise*, 37(8)1338–1344, 2005.
2. DeGroot DW, Castellani JW, Williams JO, & Amoroso PJ. Epidemiology of US Army cold weather injuries, 1980–1999. *Aviation, Space, and Environmental Medicine*, 74(5), 564-570, 2003.
3. Candler WH and Ivey H. Cold injuries among U.S. soldiers in Alaska: a five-year review. *Military Medicine*, 162(12):788-791, 1997.
4. Berko J, Ingram DD, Saha S, and Parker JD. Deaths attributed to heat, cold, and other weather events in the United States, 2006-2010. *National Health Statistics Reports*. Number 76. National Center for Health Statistics, 2014.
5. O'Donnell FL, Stahlman S, and Oetting AA. Medical Surveillance Monthly Report (MSMR). Armed Forces Health Surveillance Center; Update: Cold Weather Injuries, Active and Reserve Components, U.S. Armed Forces, July 2012–June 2017. 24(10), pp 12-21, October 2017.
6. O'Donnell FL, and Taubman SB. Medical Surveillance Monthly Report (MSMR). Armed Forces Health Surveillance Center; Update: Cold Weather Injuries, Active and Reserve Components, U.S. Armed Forces, July 2011–June 2016; 23(10), pp 12-20, October 2016.
7. Nagarajan S. Medical Surveillance Monthly Report (MSMR). Armed Forces Health Surveillance Center; Update: Cold Weather Injuries, Active and Reserve Components, U.S. Armed Forces, July 2010–June 2015; 22(10), pp 7-12, October 2015.
8. Connor RR. Medical Surveillance Monthly Report (MSMR). Armed Forces Health Surveillance Center; Update: cold weather injuries, active and reserve components, U.S. Armed Forces, July 2009–June 2014; 21(10), pp 14-19, October 2014.
9. Medical Surveillance Monthly Report (MSMR). Armed Forces Health Surveillance Center; Update: cold weather injuries, active and reserve components, U.S. Armed Forces, July 2008-June 2013; 20(10), pp 12-17, October 2013.
10. Medical Surveillance Monthly Report (MSMR). Armed Forces Health Surveillance Center; Update: Cold weather injuries, active and reserve components, U.S. Armed Forces, July 2007-June 2012; 19(10), pp 2-6, October 2012.
11. Medical Surveillance Monthly Report (MSMR). Armed Forces Health Surveillance Center; Update: Cold Weather Injuries, U.S. Armed Forces, July 2006-June 2011; 18(10), pp 14-18, October 2011.
12. Medical Surveillance Monthly Report (MSMR). Armed Forces Health Surveillance Center; Cold weather injuries, U.S. Armed Forces, July 2005-June 2010; 17(10), pp 7-11, October 2010.

13. Medical Surveillance Monthly Report (MSMR). Armed Forces Health Surveillance Center; Cold weather-related injuries, U.S. Armed Forces, July 2004- June 2009; 16(9), pp 2-6, September 2009.
14. Medical Surveillance Monthly Report (MSMR). Armed Forces Health Surveillance Center; Cold weather-related injuries, U.S. Armed Forces, July 2003-June 2008; 15(8), pp 2-6, October 2008.
15. Medical Surveillance Monthly Report (MSMR). Armed Forces Health Surveillance Center; Cold weather injuries, U.S. Armed Forces, July 2002-June 2007; 14(6), pp 12-16, September-October 2007.
16. Medical Surveillance Monthly Report (MSMR). Armed Forces Health Surveillance Center; Cold weather injuries, U.S. Armed Forces, July 2001-June 2006; 12(7), pp 14-17, October 2006.
17. Medical Surveillance Monthly Report (MSMR). Armed Forces Health Surveillance Center; Cold injuries, active component members, US Armed Forces, July 2000-June 2005; 11(5), pp 7-11, December 2005.
18. Medical Surveillance Monthly Report (MSMR). Armed Forces Health Surveillance Center; Cold injuries, active duty, US Armed Forces, July 1999-June 2004; 10(5), pp 7-11, September-October 2004.
19. Medical Surveillance Monthly Report (MSMR). Armed Forces Health Surveillance Center; Cold weather injuries, active duty, US Armed Forces, 1998-2003; 9(7), pp 7-11, November-December 2003.
20. Medical Surveillance Monthly Report (MSMR). Armed Forces Health Surveillance Center; Cold weather injuries among active duty soldiers, US Army, January 1997-July 2002; 8(7), pp 2-5, September-October 2002.
21. Medical Surveillance Monthly Report (MSMR). Armed Forces Health Surveillance Center; Cold weather injuries among active duty soldiers, US Army, 1997-2001; 7(9), pp 2-5, November-December 2001.
22. Medical Surveillance Monthly Report (MSMR). Armed Forces Health Surveillance Center; Cold weather injuries, active duty soldiers; 6(10), pp 2-3, December 2000.
23. Castellani JW, Young AJ, Ducharme MB, Giesbrecht GG, Glickman E and Sallis RE. Prevention of Cold Injuries during Exercise. *Medicine & Science in Sports & Exercise* 38: 2006.
24. Keatinge WR, and Cannon P. Freezing-point of human skin. *Lancet* I: 11-14, 1960
25. Hamlet MP. Nonfreezing cold injuries. In: *Textbook of Wilderness Medicine*, P.S. Auebach (Ed.). St. Louis, MO: Mosby, pp 129-134-2001.
26. Evans TM, Rundell KW, Beck KC, Levine AM, Baumann JM. Cold air inhalation does not affect the severity of EIB after exercise or eucapnic voluntary hyperventilation. *Medicine and Science in Sports and Exercise*; 37(4):544-549, 2005.

27. Wilber RL, Rundell KW, Szmedra L, Jenkinson DM, Im J, Drake SD. Incidence of exercise-induced bronchospasm in Olympic winter sport athletes. *Medicine & Science in Sports & Exercise*; 32(4):732-7, 2000.
28. Pozos RS & Danzl DF. Human physiological responses to cold stress and hypothermia. In: *Textbooks of Military Medicine: Medical Aspects of Harsh Environments*, Volume 1, K. B. Pandolf and R. E. Burr (Eds.). Falls Church, VA: Office of the Surgeon General, U. S. Army, pp. 351- 382, 2002.
29. ASTM International. F1291-16 Standard test method for measuring the thermal insulation of clothing using a heated manikin. 2016.
<http://www.astm.org/Standards/F1291.htm>
30. ASTM International. F2370-16 Standard test method for measuring the evaporative resistance of clothing using a sweating manikin. 2016.
<http://www.astm.org/Standards/F2370.htm>
31. Woodcock AH. Moisture transfer in textile systems, Part I. *Textile Research Journal*, 32(8), 628-633, 1962.
32. Woodcock AH. Moisture permeability index - A new index for describing evaporative heat transfer through fabric systems. Quartermaster Research and Engineering Command, Natick, MA 01702 USA, Technical Report (TR-EP-149), 1961.
33. ISO 11079. Ergonomics of the Thermal Environment—Determination and Interpretation of Cold Stress When Using Required Clothing Insulation (IREQ) and Local Cooling Effects.
34. Potter AW, Blanchard LA, Friedl KE, Cadarette BS, Hoyt RW. Mathematical prediction of core body temperature from environment, activity, and clothing: The heat strain decision aid (HSDA). *Journal of Thermal Biology*. 2017 Feb 28;64:78-85.
35. Potter AW. Method for estimating evaporative potential (im/clo) from ASTM standard single wind velocity measures. US Army Research Institute of Environmental Medicine, Natick, MA, 01760, USA, Technical Report, T16-14, 2016, ADA#637325.
36. Xu X, and Werner J. A dynamic model of the human/clothing/environment-system. *Applied Human Science: Journal of Physiological Anthropology*, 16(2), 61-75, 1997.
37. Umbach, K. H. Physiological tests and evaluation models for the optimization of the performance of protective clothing. *Environmental Ergonomics*, 139-161, 1988.
38. Gibson P, Auerbach M, Giblo J, Teal W, Endrusick T. Interlaboratory evaluation of a new sweating guarded hot plate test method (ISO 11092). *Journal of Thermal Insulation and Building Envelopes*. 1994 Oct;18(2):182-200.
39. International Organization for Standardization, International Standard ISO 11092. 2014. "Textiles-Physiological Effects, Part 1: Measurement of Thermal and Water Vapour Resistance under Steady-State Conditions (Sweating Guarded-Hotplate Test)," prepared by ISO Technical Committee ISO TC 38.
40. Xu X, Rioux TP, and Potter AW. Fabric thermal resistance and ensemble thermal resistances are two different concepts. *Journal of Occupational and Environmental Hygiene*, 11(11), D187-188, 2014.

41. Kim Y, Lee C, Li P, Corner BD, & Paquette S. Investigation of Air Gaps Entrapped in Protective Clothing System. *Fire and Materials*, 26(3), 121-126, 2002.
42. Song G. Clothing air gap layers and thermal protective performance in single layer garment. *Journal of Industrial Textiles*, 36(3), 193-205, 2007.
43. Ding D, Tang T, Song G, & McDonald A. Characterizing the performance of a single-layer fabric system through a heat and mass transfer model-Part I: Heat and mass transfer model. *Textile Research Journal*, 2010.

APPENDIX A.

US Army Extended Cold Weather Clothing Elements

| Element | Materials | Figure |
|---|--|--------|
| Silk-weight Underwear | Desert Sand 503 colored, 100% polyester, circular knit plaited jersey (Polartec Power Dry silk-weight style 9042). Plaited circular knit construction | A1 |
| Mid-weight Underwear | Desert Sand 503 colored, 93% polyester and 7% spandex circular knit plaited jersey, heavyweight jersey with stretch (Polartec Power Dry Heavyweight Jersey/Shearling Grid, Style 9110). Plaited circular knit construction. | A2 |
| Fleece Jacket | Constructed with Foliage Green 504 or Tan 499 colored, 100% virgin filament polyester fabric (Polartec Thermal Pro style 4060). Construction is double needle bar raschel warp knit, high pile, double velour. | A3 |
| Soft Shell Jacket and Trousers | Cloth for Type I is a plain weave, stretch, nylon and spandex cloth with water repellency (Nextec Application Inc., Style GLACIER). Cloth for Type II is a twill weave, aramid, cellulosic, synthetic cloth with water repellency. | A4 |
| Lightweight GORE-Tex® Jacket and Trousers | Jacket and trousers are constructed with two-layer GORE-Tex® fabric developed based on the technology of GORE-Tex® Paclite Shells. | A5 |
| Extreme Cold Weather Jacket and Trousers | Parka and trousers are constructed with an outer shell fabric that has a water resistant finish (Praetorian, Nextec Style No. 1161) and with PrimaLoft Sport Thermal bonded high-loft insulation. | A6 |

A1. Silk-weight underwear (US Ensembles)



A2. Mid-weight underwear (US Ensembles)



A3. Fleece Jacket (US Ensembles)



A4. Soft Shell Jacket and Trousers (US Ensembles)



A5. Lightweight GORE-Tex® Jacket and Trousers (US Ensembles)



A6. Extreme Cold Weather Jacket and Trousers (US Ensembles)



Canadian Cold Weather Clothing Elements

| Element | Materials | Figure |
|---------------------------------------|---|--------|
| Thermal undershirt and Long Johns | NSN: 8415-21-914-5155 | B1 |
| CADPAT Fleece jacket and trousers | NSN: 8415-21-920-8590 | B2 |
| CADPAT ICE jacket and trousers | Nylon and cotton | B3 |
| CADPAT IECS Parka | Nylon and cotton NSN: 8415-21-921-6910 / 8415-21-920-9997 | B4 |
| CADPAT IECS Bib Pants | NSN: 8415-21-913-6651 | B5 |
| Canada Goose Snow Mantra Winter parka | Outershell: 85% polyester, 15% cotton; lining: 100% nylon; neck liner: natural coyote fur; insulation: goose down | B6 |

B1. Thermal undershirt and Long Johns (Canadian Ensembles)



B2. CADPAT Fleece jacket and trousers (Canadian Ensembles)



B3. CADPAT ICE jacket and trousers (Canadian Ensembles)



B4. CADPAT IECS Parka (Canadian Ensembles)



B5. CADPAT IECS Bib Pants (Canadian Ensembles)



B6. Canada Goose Snow Mantra Winter parka (Canadian Ensembles)



Norwegian Cold Weather Clothing Elements

| Element | Materials | Figure |
|---|---|--------|
| Net underwear | 85% Rhovyl; 15% Modal | C1 |
| Wool Terry Cloth Underwear | 70% wool; 30% polyester | C2 |
| Cotton Field Shirt | 100% cotton; knitted terry cloth | C3 |
| M/02 Membrane Field Uniform (GORE-Tex®) | 3 layer membrane laminate | C4 |
| M/97 Camouflage Uniform (White) | Polyester and microfibre mixture | C5 |
| Cold Weather Jacket and Trousers | Layering of polyester and patented filling material | C6 |

C1. Net Underwear (Norwegian Ensembles)



C2. Wool Terry Cloth Underwear (Norwegian Ensembles)



C3. Cotton Field Shirt (Norwegian Ensembles)



C4. M/02 Membrane Field Uniform (GORE-Tex®) (Norwegian Ensembles)



C5. M/97 Camouflage Uniform (White) (Norwegian Ensembles)



C6. Cold Weather Jacket and Trousers (Norwegian Ensembles)

